



# **Wettability Tests of Polymer Films and Fabrics and Determination of Their Surface Energy by Contact-Angle Methods**

**by Daphne Pappas, Craig Copeland, and Robert Jensen**

**ARL-TR-4052**

**March 2007**

## **NOTICES**

### **Disclaimers**

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# **Army Research Laboratory**

Aberdeen Proving Ground, MD 21005-5069

---

**ARL-TR-4052****March 2007**

---

## **Wettability Tests of Polymer Films and Fabrics and Determination of Their Surface Energy by Contact-Angle Methods**

**Daphne Pappas, Craig Copeland, and Robert Jensen  
Weapons and Materials Research Directorate, ARL**

<b>REPORT DOCUMENTATION PAGE</b>				<i>Form Approved</i> OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. <b>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</b>					
<b>1. REPORT DATE (DD-MM-YYYY)</b> March 2007		<b>2. REPORT TYPE</b> Progress		<b>3. DATES COVERED (From - To)</b> June 2006–December 2006	
<b>4. TITLE AND SUBTITLE</b> Wettability Tests of Polymer Films and Fabrics and Determination of Their Surface Energy by Contact-Angle Methods				<b>5a. CONTRACT NUMBER</b>	
				<b>5b. GRANT NUMBER</b>	
				<b>5c. PROGRAM ELEMENT NUMBER</b>	
<b>6. AUTHOR(S)</b> Daphne Pappas, Craig Copeland, and Robert Jensen				<b>5d. PROJECT NUMBER</b> AH84	
				<b>5e. TASK NUMBER</b>	
				<b>5f. WORK UNIT NUMBER</b>	
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> U.S. Army Research Laboratory ATTN: AMSRD-ARL-WM-MA Aberdeen Proving Ground, MD 21005-5069				<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> ARL-TR-4052	
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b>				<b>10. SPONSOR/MONITOR'S ACRONYM(S)</b>	
				<b>11. SPONSOR/MONITOR'S REPORT NUMBER(S)</b>	
<b>12. DISTRIBUTION/AVAILABILITY STATEMENT</b> Approved for public release; distribution is unlimited.					
<b>13. SUPPLEMENTARY NOTES</b>					
<b>14. ABSTRACT</b> In this research, wettability testing was performed for nylon-6 and polyethylene films and ultra-high molecular weight polyethylene woven fabrics to examine the effects of surface atmospheric plasma treatment.					
<b>15. SUBJECT TERMS</b> atmospheric plasma, surface energy, contact angle, wetting, UHMWPE, nylon					
<b>16. SECURITY CLASSIFICATION OF:</b>			<b>17. LIMITATION OF ABSTRACT</b>  UL	<b>18. NUMBER OF PAGES</b>  18	<b>19a. NAME OF RESPONSIBLE PERSON</b> Daphne Pappas
<b>a. REPORT</b> UNCLASSIFIED	<b>b. ABSTRACT</b> UNCLASSIFIED	<b>c. THIS PAGE</b> UNCLASSIFIED			<b>19b. TELEPHONE NUMBER (Include area code)</b> (410) 306-0966

---

## Contents

---

<b>List of Figures</b>	<b>iv</b>
<b>List of Tables</b>	<b>iv</b>
<b>Acknowledgments</b>	<b>v</b>
<b>1. Introduction</b>	<b>1</b>
<b>2. Experimental</b>	<b>1</b>
2.1 Plasma Modification of Polymer Surfaces .....	1
2.2 Wettability Testing .....	2
<b>3. Results</b>	<b>5</b>
<b>4. Conclusions</b>	<b>8</b>
<b>5. References</b>	<b>9</b>
<b>Distribution List</b>	<b>10</b>

---

## List of Figures

---

Figure 1. Contact-angle goniometer setup at the U.S. Army Research Laboratory. ....	2
Figure 2. Wilhelmy microbalance setup for fabric liquid—solid contact-angle measurements.....	4
Figure 3. Water droplets on the control polyethylene film before plasma exposure (left) and after helium-oxygen plasma treatment (right). ....	5
Figure 4. Water contact angle vs. plasma treatment time for polyethylene films. ....	6
Figure 5. Surface energy of polyethylene and its polar and dispersive components in terms of treatment time. ....	7

---

## List of Tables

---

Table 1. Surface tension $\gamma_{LV}$ , density $\rho_L$ , and viscosity $\eta_L$ of the test liquids. ....	2
Table 2. Water contact-angle values for plasma-modified nylon films treated under helium and helium-oxygen plasmas.....	6
Table 3. Results for polyethylene woven fabric from the wettability test using the microbalance method. ....	7

---

## **Acknowledgments**

---

This research was supported in part by an appointment to the Research Participation Program at the U.S. Army Research Laboratory (ARL) administered by the Oak Ridge Institute for Science and Education through an interagency agreement between the U.S. Department of Energy and ARL.

INTENTIONALLY LEFT BLANK.



---

## 1. Introduction

---

High-strength polymer materials are a useful component in many multifunctional materials applications. However, because of low reactivity, their use is inhibited in many processing techniques. Polymer films and fibers possess low surface energies and need to be modified through surface activation prior to being used in composite systems where adhesive bonding is an issue. Treatment of polymer materials through plasma processing is one route to greatly increase surface reactivity (1, 2). Once the surface has been plasma-modified, wettability by liquids can be examined to determine the treatment effects on the polymer material's surface reactivity.

The surface energy of solids cannot be measured directly. Instead, contact angle is measured when various test liquids are placed on the solid material. Many theories have been applied to link the solid surface energy to the liquid-vapor tensions as a function of contact angle. Among the theories are the one-liquid method by Good, Girifalco, and Neumann, the two-liquid method where only dispersive and polar contributions determine the interfacial tensions, and the Lifshitz-Vanderwaals three-liquid method that considers acid-base interactions (3). As reported in literature, all methods are sensitive to the choice of test liquids used. More consistent results are obtained if a polar liquid and two or more liquids besides water are used.

In this research, wettability testing of nylon-6 (4) and polyethylene film and ultra-high molecular weight polyethylene (UHMWPE) woven fabrics was performed to examine the effects of surface plasma treatment. Each material was plasma-treated under varying treatment times, flow rates, and compositions of helium and oxygen plasmas (5).

---

## 2. Experimental

---

### 2.1 Plasma Modification of Polymer Surfaces

The atmospheric plasma system used for the surface treatments was an industrial scale plasma system from Sigma Technologies. The gases (He and He-O<sub>2</sub> in this case) were injected into the electrode at atmospheric pressure and allowed to diffuse, forming a filamentary glow discharge. Helium is typically used to initiate and generate the plasma at atmospheric pressure before another gas is introduced to the system. The operating frequency was 90 kHz with an operating power of 1050 W.

UHMWPE fibers (with an average diameter of 100  $\mu\text{m}$ ), UHMWPE films (Goodfellow, 75  $\mu\text{m}$  thick), and nylon-6 films (Goodfellow, 75  $\mu\text{m}$  thick) were exposed to the plasma created between the just described electrode and a second electrode covered by an alumina layer.

## 2.2 Wettability Testing

Wettability testing was carried out using one of two methods described in this section. For films, a static contact-angle setup using the sessile drop method was utilized. The setup consists of a micrometer-controlled syringe held in place above a moveable stage (shown in figure 1). Contact angles were recorded using a goniometer equipped with a charge-coupled-device camera and using an image capture program employing LabVIEW\* software. Contact angles were measured by defining a circle around the drop and recording the tangent angle formed at the substrate surface. The LabVIEW program measures this angle on the left and right sides of the snapshot and then averages them for a final contact-angle value.

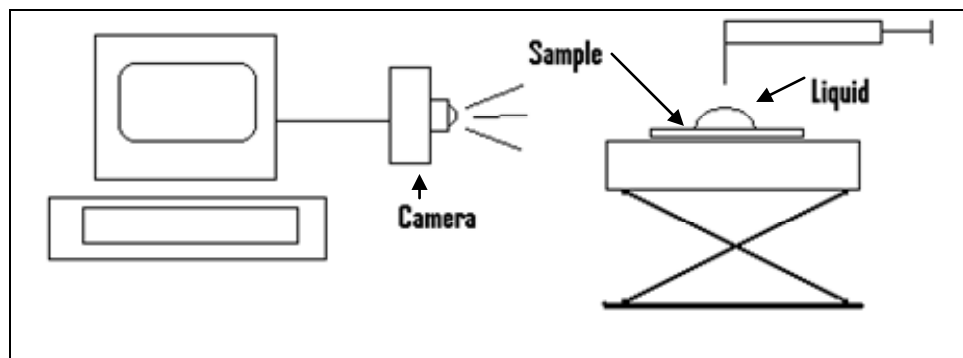


Figure 1. Contact-angle goniometer setup at the U.S. Army Research Laboratory.

For static contact-angle measurements on films, small strips ( $5 \times 1$  cm) of the sample film are cut and placed onto a glass microscope slide using double-sided tape to ensure a flat viewing surface. The glass slide is placed onto the stage where a 5- $\mu$ L drop is measured out from the syringe and dropped to the film surface. The drop is allowed to reach equilibrium before the measurement is recorded and before evaporation occurs. Once the drop has been measured, the slide is moved to allow another drop to be placed on the sample surface. We used between three and five drops for each sample, averaging the values for our final contact-angle value. This exact process was then repeated using methylene iodide, ethanol, and formamide. These liquids were chosen to cover a wide range of polarity, as listed in table 1 (6).

Table 1. Surface tension  $\gamma_{LV}$ , density  $\rho_L$ , and viscosity  $\eta_L$  of the test liquids.

Test Liquid	$\gamma_{LV}$ (mN/m)	$\rho_L$ (g/cm <sup>3</sup> )	$\eta_L$ (mPa s)
Water	72.8	0.998	1.002
Formamide	58.2	1.133	3.812
Methylene iodide	50.8	3.332	2.762
Ethanol	23.0	0.789	1.162

\* LabVIEW is a trademark of National Instruments Corporation.

The work of adhesion  $W_a$  at the interface of solid-liquid-vapor systems can be derived from the following equation:

$$W_a = \gamma_{SV} + \gamma_{LV} - \gamma_{SL}, \quad (1)$$

where  $\gamma_{SV}$  and  $\gamma_{LV}$  represent the surface energies of the solid and liquid phases, respectively, and  $\gamma_{SL}$  is the energy of the solid liquid interface. The work of adhesion represents the energy per unit area of interaction between dissimilar phases.

According to Young's equation, if  $\theta$ , the solid-liquid contact angle is known, the energy of the solid-liquid interface can be calculated using the following expression:

$$\gamma_{SL} = \gamma_{SV} - \gamma_{LV} \cos \theta. \quad (2)$$

Therefore, the combination of equations one and two leads to the determination of work of adhesion  $W_a$ :

$$W_a = \gamma_{LV} (1 + \cos \theta). \quad (3)$$

The intramolecular attraction that is expressed through  $\gamma$  consists of two components: one attributed to polar interactions,  $\gamma^p$ , and one that can be correlated to dispersion forces,  $\gamma^d$ . Fowkes stated that the intermolecular forces acting in the interface are partly a result of the London dispersive forces and that their contribution to the surface energy is represented by  $\gamma^d$ , while dipole-dipole interactions and hydrogen bond forces can be expressed through  $\gamma^p$  (7). According to Good and Girifalco (8), the attraction energy between different molecules is the geometric mean of the attraction energy between pairs of like molecules. Thus, the work of adhesion that corresponds to the interaction energy between dissimilar phases, such as in solid-liquid systems, is given as the following:

$$\begin{aligned} W_a &= W_a^d + W_a^p = 2(\gamma_{SV}^d \gamma_{LV}^d)^{1/2} + 2(\gamma_{SV}^p \gamma_{LV}^p)^{1/2} \\ \Rightarrow \frac{W_a}{2 \cdot (\gamma_{LV}^p)^{1/2}} &= (\gamma_{SV}^d)^{1/2} \left( \frac{\gamma_{LV}^d}{\gamma_{LV}^p} \right)^{1/2} + (\gamma_{SV}^p)^{1/2}. \end{aligned} \quad (4)$$

Once  $W_a$  has been calculated, a plot of  $W_a / 2(\gamma_{LV}^p)^{1/2}$  vs.  $(\gamma_{LV}^d / \gamma_{LV}^p)^{1/2}$  for multiple test liquids will yield a linear fit with slope of  $(\gamma_{SV}^d)^{1/2}$  and intercept equaling  $(\gamma_{SV}^p)^{1/2}$ . Squaring and adding these two values gives the total surface tension of the solid.

When measuring the liquid-solid contact angle for fabrics, the static contact-angle setup can't be used, as fabric roughness causes absorption of the single drop. To measure the liquid-solid contact angle for fabrics, we use the Wilhelmy balance method setup. This setup consists of a LabVIEW interface allowing for computer control of a moveable stage and simultaneous reading from a microbalance.

For fabric testing using the Wilhelmy balance setup (shown in figure 2), small, equal-width strips of each fabric to be tested are cut and attached by tape to a straight piece of wire with a hooked opposite end. This wire is suspended from the underside of the microbalance, which must then be tared. Single fiber tests are not preferred because extraction of a single fiber may result in an uneven distribution of finishes and sizings. A small vessel of testing liquid is placed on the moveable stage directly beneath the hanging fabric strip, ~1 mm from the fabric end. The stage is then moved upward toward the fabric at a speed of 10  $\mu\text{m/s}$ . Immediately upon liquid-solid contact, which must be viewed directly, the stage progression is stopped. This leaves the sample edge only a few micrometers below the liquid surface. As the sample is partially immersed in a liquid, the liquid either rises or depresses along the strip, resulting in a wetting force  $F_w$  on the solid (9):

$$F_w = \gamma_{LV} P \cos \theta, \quad (5)$$

where  $\gamma_{LV}$  is the surface tension of the liquid,  $P$  is the perimeter dimension of the solid-liquid interface, and  $\theta$  is the contact angle between liquid and solid interface.

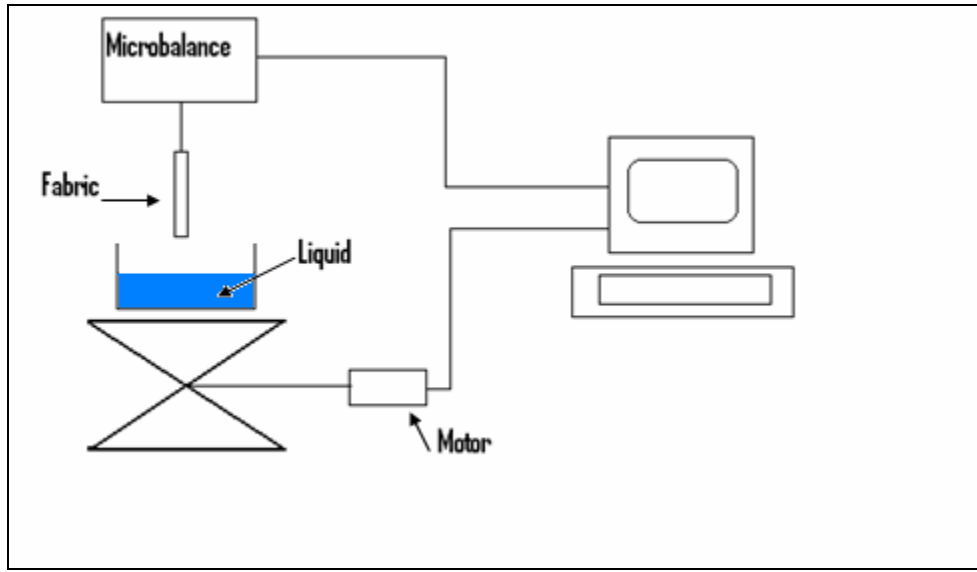


Figure 2. Wilhelmy microbalance setup for fabric liquid—solid contact-angle measurements.

The perimeter  $P$  can be derived from equation 5 from the force measurement in a total wetting liquid, such as hexane, where  $\cos \theta = 1$ . The microbalance will display a mass reading that is due to liquid uptake and the wetting force exerted on the perimeter of the fabric by the liquid. To attain an accurate value for the wetting force, liquid uptake must be subtracted from the force value given by the microbalance. To accomplish this, liquid uptake must be allowed to continue to saturation, at which point the microbalance reading will be nearly stable. This value is the advancing steady-state force  $F_{ADV}$ . The stage is then moved down at 80  $\mu\text{m/s}$  until the fabric is free of the liquid surface. As soon as separation occurs, the mass value must again be taken,

corresponding to the total liquid retention  $W_t$ . The wetting force  $F_W$  is then given by the following:

$$F_W = F_{ADV} - W_t. \quad (6)$$

Combined with equation 5, the contact angles between the fabric and the various test liquids are obtained.

### 3. Results

Polyethylene films were exposed to helium plasmas containing oxygen at atmospheric pressure conditions. The total helium flow was 15,000 sccm\*, and oxygen was diluted in it in the following volume percentages: 0.6%, 2%, and 6%. Through the collisions and reactions occurring in the gas phase, atomic oxygen is generated that is highly reactive and causes oxidation and mild etching of the polymer surface. X-ray photoelectron spectroscopy (XPS) studies (5) show that hydroxylic and carboxylic functionalities are grafted on the surface, modifying its chemical character.

Besides functionalizing the surface, these polar groups are expected to decrease the water contact angle of the surface (compared to the control sample) and increase its energy. Figure 3 depicts the effect of plasma exposure on a polyethylene film. Prior to plasma exposure, a drop of water was placed on the film and the contact angle was 98°. In this case, the surface can be characterized as hydrophobic. Then, the film was treated under a helium-oxygen plasma for a few seconds and the water contact angle dropped to 25°, revealing a very hydrophilic surface.

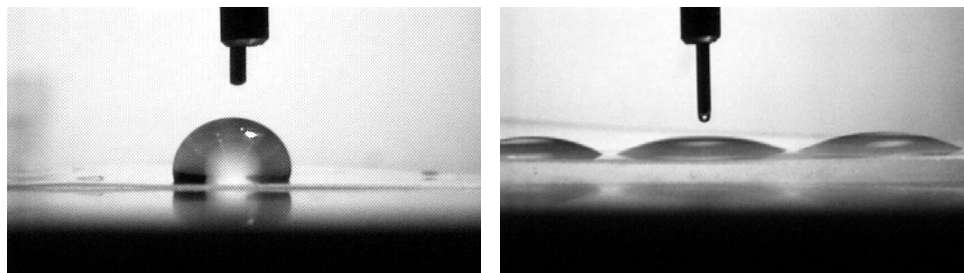


Figure 3. Water droplets on the control polyethylene film before plasma exposure (left) and after helium-oxygen plasma treatment (right).

Figure 4 shows the observed water contact angles for the three polyethylene films treated under helium-oxygen plasmas and the film treated under pure helium plasma.

\* sccm = standard cubic centimeters per minute.

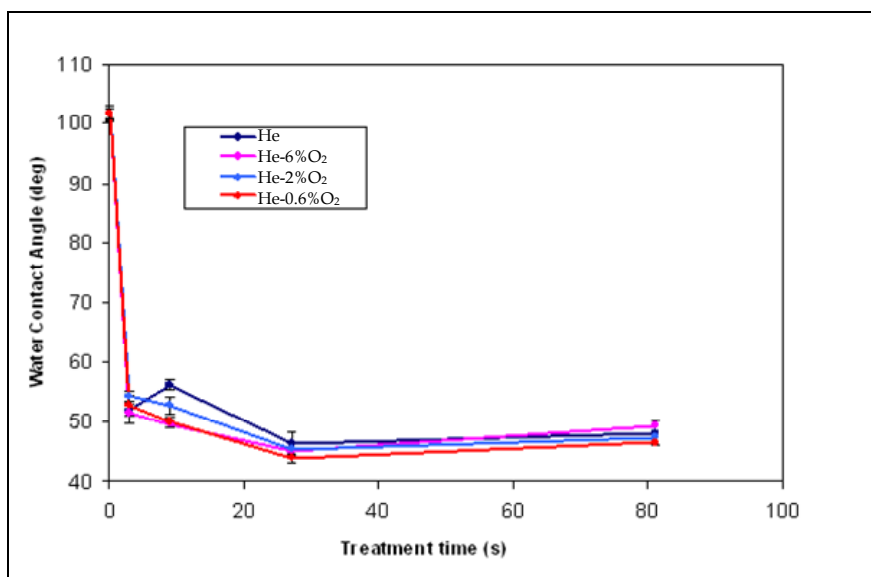


Figure 4. Water contact angle vs. plasma treatment time for polyethylene films.

The water contact angles were measured directly following the plasma exposure. The water contact angle for the control sample was 102°. After a short plasma treatment of 3 s, it decreased to 52°. The recorded values are similar for all samples studied, indicating that under these experimental conditions (power, gas composition, gas flow) the plasma has similar impact on the treated surfaces. The reduction of the water contact angle is a result of two combined effects due to the plasma exposure: chemical modification (oxidation) of the surface as described earlier and morphological changes on the surface as a rougher surface is created.

Similar results were found for nylon-6 films treated under He-O<sub>2</sub> plasmas, as shown in table 2. In this case, the average water contact angle for the control sample was found to be 75° and depending on the gas composition and treatment time, the contact angle of the modified surface can be as low as 26.4°.

Table 2. Water contact-angle values for plasma-modified nylon films treated under helium and helium-oxygen plasmas.

Gas	Treatment Time (s)			
	3	9	27	81
He-0%O <sub>2</sub>	43.2° ± 0.9°	37.5° ± 0.5°	29.8° ± 0.2°	26.4° ± 1.2°
He-6%O <sub>2</sub>	47.2° ± 0.3°	36.1° ± 1.5°	34.3° ± 0.2°	35.5° ± 0.9°
He-2%O <sub>2</sub>	44.5° ± 0.7°	41.4° ± 1.0°	39.3° ± 1.6°	32.4° ± 1.1°
He-0.6%O <sub>2</sub>	41.6° ± 1.6°	37.3° ± 1.2°	35.7° ± 0.5°	31.6° ± 1.9°

The static contact-angle measurements are then used to calculate the surface tension of the polymer films. The theory described in section 2.2 was used to calculate the surface tension of polyethylene films using three test liquids. Plotting equation (4) allowed us to calculate the two components of the film surface energy,  $\gamma^p$  and  $\gamma^d$ . Then, the total surface tension for each sample was calculated, and the results were plotted in terms of treatment time. As seen in figure 5, we observed a significant increase of the polar component  $\gamma^p$  depending on the plasma treatment time, which ranged from 3 to 30 s. The dispersive component  $\gamma^d$  shows a small decrease and remains stable for longer exposure times. The steep increase of the polar component of the surface energy reveals that new polar groups are grafted on the film surface, as confirmed earlier by XPS results, and are responsible for the improved hydrophilicity of the surface.

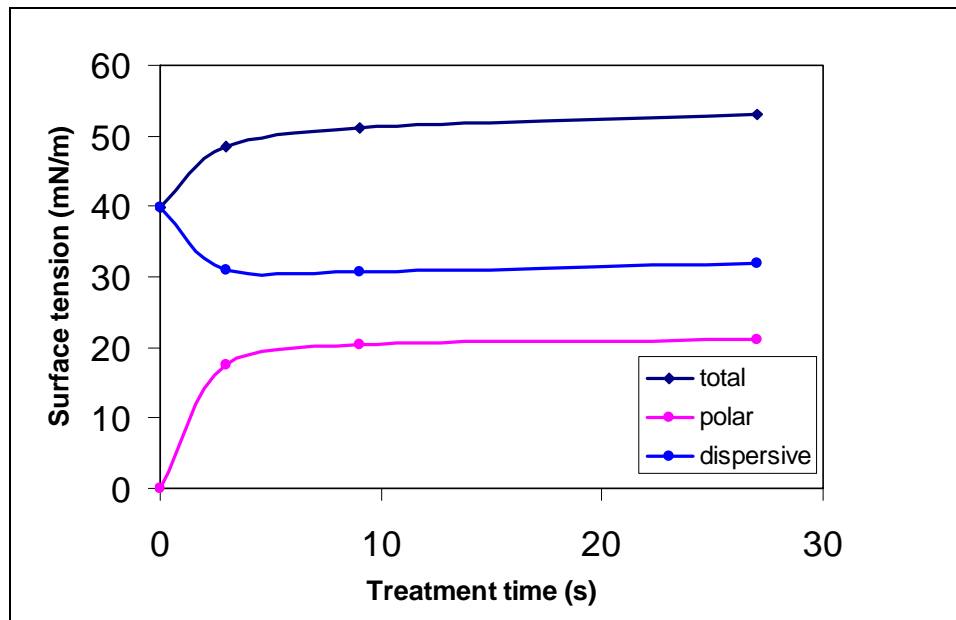


Figure 5. Surface energy of polyethylene and its polar and dispersive components in terms of treatment time.

Wettability studies on UHMWPE woven fabrics were also performed. Small strips of the material were cut and immersed in water, methylene iodide, and ethanol, while a microbalance monitored the total force and liquid uptake. The wetting force and, finally, the contact angles were calculated using the theory in section 2.2; the results are shown in table 3. The water contact angle of polyethylene fibers was  $65^\circ$  and decreased to  $23.7^\circ$  for ethanol, as expected.

Table 3. Results for polyethylene woven fabric from the wettability test using the microbalance method.

Test Liquid	Wetting Force $F_w$ ( $10^{-4}$ N)	Contact Angle
Water	$5.99 \pm 0.21$	$64.3^\circ \pm 1.0^\circ$
Methylene iodide	$5.62 \pm 0.30$	$54.4^\circ \pm 2.2^\circ$
Ethanol	$3.89 \pm 0.06$	$22.2^\circ \pm 2.0^\circ$

---

## **4. Conclusions**

---

Two different wettability test methods were applied at U.S. Army Research Laboratory to measure and calculate liquid-polymer contact angles and polymer surface tension. The polymeric materials studied were polyethylene and nylon thin films and polyethylene woven fabric. For the films, three to five drops of each test liquid was averaged, giving consistent results for the liquid-solid contact angle and providing data for the surface tension calculation. Results obtained for the control films were compared with those of the plasma-modified surfaces, proving that the surface chemistry is altered and more hydrophilic surfaces are formed through plasma exposure. For the woven fabrics, small strips of the control fabrics were tested, and the microbalance method was employed to give an estimate of the liquid-solid contact angle.



---

## 5. References

---

1. Chan, C. M.; Ko, T. M.; Hiraoka, H. Polymer Surface Modification by Plasmas and Photons. *Surf. Sci Report* **1996**, *24*, 1–54.
2. DePiero, W.; Brescia, J.; Martinelli, D. *Plasma Treatment of Plastics and Composite Materials: A Surface Preparation for Adhesive Bonding*; ARAED-TR-94016; U.S. Army Armament Research, Development and Engineering Center: Picatinny Arsenal, NJ, 1995.
3. Mykhaylyk, T.; Evans, S.; Fernyhough, C.; Hamley, I.; Henderson, J. Surface Energy of Ethylene-Co-1-Butene Copolymers Determined by Contact Angle Methods. *J. Coll. Interf. Sci.* **2003**, *260*, 234–239.
4. Pappas, D.; Bujanda, A.; Demaree, J.; Hirvonen, J.; Kosik, W.; Jensen, R.; McKnight, S. Surface Modification on Polyamide Fibers and Films Using Atmospheric Plasmas. *Surf. Coat. Technol.* **2006**, *201*, 4384–4388.
5. Pappas, D.; Kosik, W.; Bujanda, A.; Demaree, J.; Hirvonen, J.; Orlicki, J.; Jensen, R. McKnight, S. *Nanotexturing of High Performance Woven Fabrics for Novel Composite Applications*, 25th Army Science Conference, Orlando, FL, 27–30 November 2006.
6. Aranberri-Askagorta, I.; Lampke, T.; Bismarck, A. Wetting Behavior of Flax Fibers as Reinforcement for Polypropylene. *J. Coll. Interf. Sci.* **2003**, *263*, 580–589.
7. Fowkes, F. Predicting Attractive Forces at Interfaces. *Industr. Engin. Chem* **1964**, *56*, 12, 40–53.
8. Good, R.; Girifalco, L. A Theory for Estimation of Surface and Interfacial Energies. III Estimation of Surface Energies of Solids from Contact Angle Data. *J. Phys. Chem.* **1960**, *64*, 561–565.
9. Hsieh, Y.; Yu, B. Liquid Wetting, Transport, and Retention Properties of Fibrous Assemblies, Part 1: Water Wetting Properties of Woven Fabrics and Their Constituent Single Fibers. *Textile Res. J.* **1992**, *62*, 677–685.

NO. OF  
COPIES ORGANIZATION

1 DEFENSE TECHNICAL  
(PDF INFORMATION CTR  
ONLY) DTIC OCA  
8725 JOHN J KINGMAN RD  
STE 0944  
FORT BELVOIR VA 22060-6218

1 US ARMY RSRCH DEV &  
ENGRG CMD  
SYSTEMS OF SYSTEMS  
INTEGRATION  
AMSRD SS T  
6000 6TH ST STE 100  
FORT BELVOIR VA 22060-5608

1 DIRECTOR  
US ARMY RESEARCH LAB  
IMNE ALC IMS  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

3 DIRECTOR  
US ARMY RESEARCH LAB  
AMSRD ARL CI OK TL  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

ABERDEEN PROVING GROUND

1 DIR USARL  
AMSRD ARL CI OK TP (BLDG 4600)